

## A Metal–Organic Framework with Entatic Metal Centers Exhibiting High Gas Adsorption Affinity

Shengqian Ma and Hong-Cai Zhou\*

Department of Chemistry & Biochemistry, Miami University, Oxford, Ohio 45056

Received May 20, 2006; E-mail: zhouh@muohio.edu

The lack of an effective, economic, and safe on-board vehicular gas (hydrogen or methane) storage method is one of the major technical barriers preventing fuel-cell driven automobiles to compete with traditional ones.<sup>1</sup> Recently, the gas-storage properties of metal–organic frameworks (MOFs) have been actively explored.<sup>2</sup> In the area of hydrogen storage, suggested strategies to increase hydrogen uptake include using pore sizes comparable to gas molecules<sup>3</sup> and introducing coordinatively unsaturated metal centers.<sup>4</sup> Both strategies boil down to the enhancement of gas affinity of the material. Recent inelastic neutron scattering studies suggest that high-affinity H<sub>2</sub> binding sites are metal-based.<sup>5</sup> These recent findings prompted us to search for new ways to increase the gas affinity of metal centers in MOFs.


In metalloproteins, such as hemoglobin, reversible O<sub>2</sub> binding is achieved by utilizing an iron active center (Figure 1a), where a porphyrin ligand and a histidine residue force the iron center into a square pyramidal geometry, generating an open coordination site for gas binding. Similarly, in Vitamin B<sub>12</sub> (VB<sub>12</sub>), the central cobalt is surrounded by a corrin and a proximal ligand, and the distal position is open for substrate binding.<sup>6</sup> Herein we report a MOF with a novel secondary building unit (SBU, Figure 1b), containing four hemoglobin/VB<sub>12</sub>-like cobalt centers bundled through sharing a  $\mu_4$ -oxo bridge, producing four metal centers at an entatic state (vide infra) for gas binding. This MOF exhibits exceptional gas adsorption affinity for a number of gases.

In bioinorganic chemistry, an entatic state is a state in which an unusual geometry is imposed by the protein polypeptides on a metal center whose reactivity in electron transfer, substrate binding, or catalysis is enhanced.<sup>7</sup> Similarly, due to the specific geometric requirements of the ligands and SBUs in a MOF, the metal centers can be forced into an entatic state to enhance their affinity toward gases.


Entatic metal centers (EMCs) represent a biomimetic approach to coordinatively unsaturated metal centers (UMCs).<sup>8</sup> The latter are frequently obtained by removal of one or more ligands from a metal center to achieve coordinative unsaturation; the ligand removal required to achieve UMCs may collapse the entire network.<sup>9</sup> Conversely, most of the EMCs are ready for substrate binding without the need for ligand removal.

Herein we report a MOF with EMCs, H<sub>2</sub>[Co<sub>4</sub>O(TATB)<sub>8/3</sub>], designated PCN-9 (Porous Coordination Network) for convenience. TATB (4,4',4''-s-triazine-2,4,6-triyltribenzoate) is a ligand developed in this laboratory for its planar conformation, potential ability to bind additional metal atoms, and high thermal stability of resulting MOFs.<sup>4b,10</sup> PCN-9 crystals were grown under solvothermal conditions by a reaction between H<sub>3</sub>TATB and cobalt nitrate in DMSO at 135 °C.

X-ray single-crystal analysis<sup>11</sup> revealed that PCN-9 crystallizes in the *Im* $\bar{3}m$  space group. It adopts a square-planar Co<sub>4</sub>( $\mu_4$ -O) SBU, with a  $\mu_4$ -oxo residing at the center of a square of four Co atoms. All four Co atoms in the SBU are five-coordinate with square-

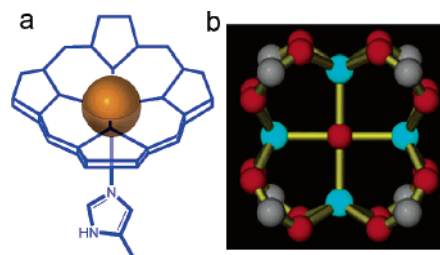

**Figure 1.** (a) Schematic drawing of the active center of hemoglobin. The gold sphere represents an Fe atom. (b) The Co<sub>4</sub>( $\mu_4$ -O)(carboxylate)<sub>4</sub> SBU found in PCN-9. Color scheme: C, gray; Co, aqua; and O, red.

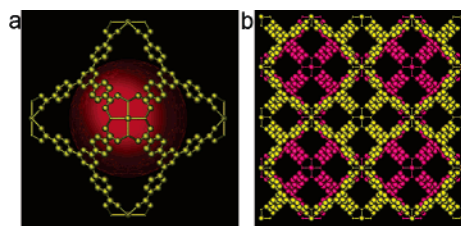

**Figure 2.** (a) Crystal structure of PCN-9 showing an octahedral cage; the red sphere represents void inside the cage. (b) View of the crystal structure of PCN-9 along the *a*-axis; the two interpenetrated networks are shown in gold and pink, respectively. All atoms are shown in arbitrary scales.

pyramidal geometry. The Co– $\mu_4$ -O distance is 2.351(2) Å. If one of the five-coordinate Co atoms is compared to the active center in hemoglobin, the  $\mu_4$ -O is analogous to the proximal ligand, and on the opposite side of the square-pyramidal base is the distal position of the Co, which is below the plane of the four O atoms in an entatic state, and ready to bind a substrate to achieve octahedral coordination. Although a tetrahedral  $\mu_4$ -oxo bridge is common,<sup>12</sup> a square-planar  $\mu_4$ -oxo bridge is rare. Only a few examples have been found in iron,<sup>13a</sup> copper,<sup>13b</sup> vanadium,<sup>13c</sup> and niobium<sup>13d</sup> compounds. The square-planar  $\mu_4$ -oxo bridge found in PCN-9 is unique in a MOF. Every Co<sub>4</sub>( $\mu_4$ -O) SBU connects eight trigonal-planar TATB ligands, and every TATB ligand connects three Co<sub>4</sub>( $\mu_4$ -O) SBUs to form a (8,3)-net. Alternatively, this (8,3)-net can also be described as a three-dimensional network formed by corner sharing of octahedral cages (Figure 2a); the *O<sub>h</sub>*-cage is defined by six Co<sub>4</sub>( $\mu_4$ -O) SBUs at the corners and eight TATB ligands on the faces. Overall, the structure of PCN-9 can be obtained by the interpenetration of two (8,3)-nets, the second being generated through translation along [1 1 0].

The volume of the octahedral cage is 2740 Å<sup>3</sup>. Each open window of the cage is 6.7 × 6.7 Å (atom to atom distance) and possesses two EMCs with distal sites pointing toward the void. The solvent accessible volume of PCN-9 calculated using PLATON<sup>14</sup> is 58.8%. The permanent porosity of PCN-9 is confirmed by its N<sub>2</sub> adsorption isotherm. After desolvation, PCN-9 exhibits a Langmuir surface area of 1355 m<sup>2</sup>/g and a pore volume of 0.51 cm<sup>3</sup>/g.

To determine the gas affinity of PCN-9, adsorption isotherms were collected at various temperatures, and the data were fit using the Langmuir–Freundlich equation.<sup>15</sup> Isothermic adsorption enthalpies as a function of the quantity of gas adsorbed were calculated using a variant of the Clausius–Clapeyron equation.<sup>16,18a,b</sup>

At low coverage, PCN-9 exhibits an O<sub>2</sub> adsorption enthalpy of 17.8 kJ/mol, comparable to that of Co exchanged zeolites (15.1–18.5 kJ/mol).<sup>17</sup> Similarly, at low coverage, the CO adsorption enthalpy of PCN-9 reaches 21.0 kJ/mol. These results represent the first measurement of O<sub>2</sub> or CO adsorption enthalpy in MOFs.

H<sub>2</sub> adsorption isotherm at 77 K indicates that PCN-9 has an uptake of 1.53 wt % at 760 Torr. Hydrogen adsorption isotherms at two other temperatures were collected and used to calculate the heat of adsorption. At low coverage, the heat of adsorption of PCN-9 for H<sub>2</sub> is 10.1 kJ/mol, which is higher than that of MOF-5 (5.2 kJ/mol), Prussian blue (7.4 kJ/mol), MOF-74 (8.3 kJ/mol), or HKUST-1 (6.6 kJ/mol) and is comparable to that of IRMOF-11 (9.1 kJ/mol) or a magnesium MOF (9.5 kJ/mol).<sup>18</sup>

In VB<sub>12</sub>, the active center can bind a methyl or an alkyl group.<sup>6</sup> It is expected that PCN-9, with its SBUs structurally similar to the active center of VB<sub>12</sub>, should have a high methane affinity. The CH<sub>4</sub> isotherms of PCN-9 at three temperatures were collected, corresponding to an adsorption enthalpy of 23.3 kJ/mol at low coverage. To the best of our knowledge, this is by far the highest CH<sub>4</sub> adsorption enthalpy found among MOFs (IRMOF-6 = 12.1 kJ/mol, MIL-53 = 17 kJ/mol).<sup>19</sup>

To further confirm that this remarkable enhancement of gas affinity is due to the EMCs, freshly prepared PCN-9 crystals (or a guest-free sample) were soaked in a dilute tetrabutylammonium cyanide solution in THF (1 mg/mL) for 2 days until the color of the crystals changed from violet to dark red. An IR spectra using this dark-red polycrystalline sample showed a sharp peak at 2105 cm<sup>-1</sup>, a +50 cm<sup>-1</sup> shift of the C≡N stretch relative to that of free cyanide, consistent with the literature value for terminal cyanides bound to Co atoms.<sup>20</sup>

Aware that the bulkiness of the counterion may prevent cyanide ions from permeating into the channels, we decided to use CO as an IR probe. A guest-free PCN-9 sample was kept under a CO atmosphere (3 bar) overnight. IR spectra of the sample showed a peak at 2044 cm<sup>-1</sup> (compared to 2143 cm<sup>-1</sup> for free CO),<sup>21</sup> indicating terminal CO binding to the EMCs. The same sample was then kept under dynamic vacuum for 0.5 h to remove CO guests. The 2044 cm<sup>-1</sup> feature disappeared, demonstrating the reversibility of EMC binding, consistent with CO adsorption measurements.

In summary, EMCs have been created based on the geometric requirements of a MOF. This approach is analogous to the formation of protein EMCs, which are enforced by surrounding polypeptides. The EMC-containing MOF possesses exceptionally high affinity to a number of commercially relevant gases. In particular, the H<sub>2</sub> and CH<sub>4</sub> adsorption enthalpies of PCN-9 are among the highest reported thus far. The biomimetic strategy presented here will be generally applicable in the search of new adsorptive materials to meet the requirements of on-board vehicular gas storage.

Additionally, the EMCs inside the open channels of PCN-9 make them ideal candidates for size- and/or shape-selective catalysis. This line of research is currently underway in our laboratory.

**Acknowledgment.** This work was supported by the National Science Foundation (CHE-0449634) and Miami University. H.C.Z. acknowledges the Research Corporation for a Research Innovation Award and a Cottrell Scholar Award.

**Supporting Information Available:** Detailed experimental procedures, X-ray structural data, thermogravimetric analysis, and gas adsorption data. This material is available free of charge via the Internet at <http://pubs.acs.org>.

## References

- (1) (a) Hoogers, G., Ed. *Fuel Cell Technology Handbook*; CRC Press LLC: Boca Raton, FL, 2003. (b) Schlappbach, L.; Zuttel, A. *Nature* **2001**, *414*, 353. (c) Hydrogen, Fuel Cells & Infrastructure Technologies Program: Multi-year Research, Development, and Demonstration Plan. U.S. Department of Energy, 2005, <http://www.eere.energy.gov/hydrogenandfuelcells/mypp/>.
- (2) (a) Rowsell, J. L. C.; Yaghi, O. M. *Angew. Chem., Int. Ed.* **2005**, *44*, 4670. (b) Wong-Foy, A. G.; Matzger, A. J.; Yaghi, O. M. *J. Am. Chem. Soc.* **2006**, *128*, 3494.
- (3) Pan, L.; Sander, M. B.; Huang, X.; Li, J.; Smith, M. R., Jr.; Bittner, E. W.; Brockrath, B. C.; Johnson, J. K. *J. Am. Chem. Soc.* **2004**, *126*, 1308.
- (4) (a) Chen, B. L.; Ockwig, N. W.; Millward, A. R.; Contreras, D. S.; Yaghi, O. M. *Angew. Chem., Int. Ed.* **2005**, *44*, 4745. (b) Sun, D.; Ma, S.; Ke, Y.; Collins, D. J.; Zhou, H.-C. *J. Am. Chem. Soc.* **2006**, *128*, 3896. (c) Yang, Q.; Zhong, C. *J. Phys. Chem. B* **2006**, *110*, 655.
- (5) (a) Rosi, N. L.; Eckert, J.; Eddaoudi, M.; Vodak, D. T.; Kim, J.; O'Keeffe, M.; Yaghi, O. M. *Science* **2003**, *300*, 1127. (b) Rowsell, J. L. C.; Eckert, J.; Yaghi, O. M. *J. Am. Chem. Soc.* **2005**, *127*, 14904.
- (6) Lippard, S. J.; Berg, J. M. *Principles of Bioinorganic Chemistry*; University Science Books: Mill Valley, CA, 1994.
- (7) (a) Vallee, B. L.; Williams, R. J. P. *Proc. Natl. Acad. Sci. U.S.A.* **1968**, *59*, 498. (b) Darensbourg, M. Y.; Lyon, E. J.; Zhao, X.; Georgakaki, I. P. *Proc. Natl. Acad. Sci. U.S.A.* **2003**, *100*, 3683. (c) Williams, R. J. P. *Eur. J. Biochem.* **1995**, *234*, 363.
- (8) (a) Kitaura, R.; Onoyama, G.; Sakamoto, H.; Matsuda, R.; Noro, S.; Kitagawa, S. *Angew. Chem., Int. Ed.* **2004**, *43*, 2684. (b) Chen, B.; Eddaoudi, M.; Reineke, T. M.; Kampf, J. W.; O'Keeffe, M.; Yaghi, O. M. *J. Am. Chem. Soc.* **2000**, *122*, 11559. (c) Kitagawa, S.; Noro, S.; Nakamura, T. *Chem. Commun.* **2006**, 701.
- (9) Ke, Y.; Collins, D. J.; Sun, D.; Zhou, H.-C. *Inorg. Chem.* **2006**, *45*, 1897.
- (10) Sun, D.; Ma, S.; Ke, Y.; Petersen, T. M.; Zhou, H. *Chem. Commun.* **2005**, 2663.
- (11) X-ray crystal data for PCN-9: Co<sub>4</sub>C<sub>64</sub>H<sub>32</sub>N<sub>8</sub>O<sub>17</sub>, fw = 1420.70, cubic, *Im*3m, *a* = 25.4387(5) Å, *b* = 25.4387(5) Å, *c* = 25.4387(5) Å, *V* = 16462.1(6) Å<sup>3</sup>, *Z* = 6, *T* = 293 K, ρ<sub>calcd</sub> = 0.86 g/cm<sup>3</sup>, *R*<sub>1</sub> (*I* > 2σ(*I*)) = 0.103, *wR*<sub>2</sub> (all data) = 0.307.
- (12) Jaitner, P.; Ricker, C.; Wurst, K. *Chem. Commun.* **1997**, 1245.
- (13) (a) Nair, V. S.; Hagen, K. S. *Inorg. Chem.* **1994**, *33*, 185. (b) Samuels, J. A.; Vaartstra, B. A.; Huffman, J. C.; Trojan, K. L.; Hatfield, W. E.; Caulton, K. G. *J. Am. Chem. Soc.* **1990**, *112*, 9623. (c) Rambo, J. R.; Huffman, J. C.; Christou, G. *J. Am. Chem. Soc.* **1989**, *111*, 8027. (d) Cotton, F. A.; Shang, M. *J. Am. Chem. Soc.* **1990**, *112*, 1584.
- (14) Spek, A. L. *PLATON, A Multipurpose Crystallographic Tool*; Utrecht University: Utrecht, The Netherlands, 2001.
- (15) Yang, R. T. *Gas Adsorption by Adsorption Processes*; Butterworth: Boston, 1997.
- (16) Roquerol, F.; Rouquerol, J.; Sing, K. *Adsorption by Powders and Solids: Principles, Methodology, and Applications*; Academic Press: London, 1999.
- (17) Sebastian, J.; Jasra, R. V. *Ind. Eng. Chem. Res.* **2005**, *44*, 8014.
- (18) (a) Kaye, S. S.; Long, J. R. *J. Am. Chem. Soc.* **2005**, *127*, 6506. (b) Dincă, M.; Long, J. R. *J. Am. Chem. Soc.* **2005**, *127*, 9376. (c) Rowsell, J. L. C.; Yaghi, O. M. *J. Am. Chem. Soc.* **2006**, *128*, 1304.
- (19) (a) Düren, T.; Sarkisov, L.; Yaghi, O. M.; Snurr, R. Q. *Langmuir* **2004**, *20*, 2683. (b) Bourrelly, S.; Llewellyn, P. L.; Serre, C.; Millange, F.; Loiseau, T.; Férey, G. *J. Am. Chem. Soc.* **2005**, *127*, 13519.
- (20) Cotton, F. A.; Wilkinson, G.; Murillo, C. A.; Bochmann, M. *Advanced Inorganic Chemistry*, 6th ed.; John & Wiley & Sons: New York, 1999.
- (21) Elschenbroich, C. *Organometallics*, 3rd ed. (in English); Wiley-VCH: Weinheim, Germany, 2005.

JA063538Z